



Production and Characterization of bacterial cellulose from *Komagataeibacter xylinus* S4 strain

Komagataeibacter xylinus S4 suşundan bakteriyel selüloz üretimi ve karakterizasyonu

Nazime Mercan DOĞAN¹, Burak TOP¹, Naime Nur BOZBEYOĞLU², Duygu TAKANOGLU BULUT³, Orhan KARABULUT⁴, Erdal UGUZDOĞAN^{5*}

¹Department of Biology, Faculty of Arts and Science, Pamukkale University, Denizli, Turkey.

nmercant@pau.edu.tr, buraktop@hotmail.com

²Plant and Animal Production Department, Tavas Vocational High School, Pamukkale University, Denizli, Turkey.

nbozbeoyglu@pau.edu.tr

³Application of Advanced Technology and Research Center (iltam), Pamukkale University, Denizli, Turkey.

dbulut@pau.edu.tr

⁴Department of Physics, Faculty of Arts And Science, Pamukkale University, Denizli, Turkey.

okarabulut@pau.edu.tr

⁵Department of Chemical Engineering, Faculty of Engineering, Pamukkale University, Denizli, Turkey.

erdalu@pau.edu.tr

Received/Geliş Tarihi: 05.01.2023

Revision/Düzeltilme Tarihi: 06.05.2023

doi: 10.5505/pajes.2023.25256

Accepted/Kabul Tarihi: 16.05.2023

Research Article/Araştırma Makalesi

Abstract

In this study, bacterial cellulose (BC) was obtained from *Komagataeibacter xylinus* S4 and characterized in detail. The effects of a various of carbon sources and media, different pH conditions, incubation temperatures, surface area/volume ratios, and incubation durations were determined for BC production. Considering the carbon types, the amount of BC production from high to low was realized as sucrose, fructose, mannitol, xylose, arabinose, and lactose. The highest BC amount (1.303 g/L) was achieved by combining M1A05P5 broth, 30 °C, 1.06 cm⁻¹ surface area/volume ratio, pH 3.5 and 21 days. According to scanning electron microscope (SEM) analysis, the cellulose fibril diameters were 34.87-45.97 nm at pH 3.5 and 29.71-102.3 nm at pH 6.5 in M1A05P5. Also, TGA analysis exhibited that the weight loss of BC in the removal of water step initialized between 50 °C and 150 °C and the degradation step initialized between 215 °C and 228 °C. Finally, the electrical conductivity values of the BC samples were determined on the 27-137 °C temperature scale. It was observed that the conductivity was temperature dependent, and the conductivity increased exponentially as the temperature increased. In conclusion, the cellulose from *K. xylinus* S4 typically showed a semiconducting behavior.

Keywords: Bacterial cellulose, Local isolate, Carbon sources, Electrical conductivity, Thermal analysis, SEM.

Öz

Bu çalışmada, *Komagataeibacter xylinus* S4'ten elde edilen bakteriyel selüloz (BS) detaylı şekilde karakterize edilmiştir. Çeşitli karbon kaynakları ve ortamlarının, farklı pH şartları, sıcaklıklar, yüzey alanı/hacim oranları ve inkübasyon zamanlarının BS üretimi etkisi tespit edilmiştir. Karbon tipleri gözönüne alındığında, yüksekten düşüğe doğru BS üretim miktarı, sükröz, fruktoz, mannitol, ksiloz, arabinoz ve laktöz şeklinde gerçekleşmiştir. En yüksek BS miktarına (1.303 g/L), M1A05P5 sıvı besiyeri, 30 °C sıcaklık, 1.06 cm⁻¹ yüzey alanı/hacim oranı, pH 3.5 ve 21 günlük kombinasyonda ulaşılmıştır. Taramalı elektron mikroskobu (SEM) analizine göre M1A05P5 ortamında üretilen bakteriyel selüloz liflerinin çapları pH 3.5'te 34.87-45.97 nm değerindeyken pH 6.5 değerine yükseldiğinde lif çapları 29.71-102.3 nm olarak ölçülmüştür. Ayrıca, TGA analizi, BS numunelerinde dehidrasyon adımındaki ağırlık kaybının 50 °C ile 150 °C arasında, bozunma adımının ise 215 °C ile 228 °C arasında başladığını göstermiştir. Son olarak, BS örneklerinin elektriksel iletkenlik değerleri 27-137 °C sıcaklık skalasında tespit edildi. İletkenliğin sıcaklığa bağlı olduğu ve sıcaklık arttıkça iletkenliğin üstel olarak arttığı gözlemlendi. Sonuç olarak, *K. xylinus* S4 selülozu tipik olarak yarı iletken bir davranış göstermiştir.

Anahtar kelimeler: Bakteriyel selüloz, Yerel izolat, Karbon kaynakları, Elektriksel iletkenlik, Termal analiz, SEM.

1 Introduction

Cellulose is a biodegradable and abundant polysaccharide found in nature. Also, it is a renewable and biocompatible polymer [1]-[5]. Although cellulose is obtained from plant sources, it is also secreted by bacteria, fungi, and algae. Bacterial cellulose (BC) is known possess notable characteristics compared to cellulose from plants in terms of various properties such as purity, macromolecular properties, water holding capacity, and total surface area [4],[6]-[9]. Moreover, there are also some disadvantages to obtaining cellulose from plants, such as cutting trees and removing lignin,

pectin, and hemicellulose [10]-[13]. *Acetobacter xylinum* is the first bacterium reported to produce cellulose. Studies over the years have demonstrated the cellulose production capabilities of Gram-negative and Gram-positive bacteria [5],[14]-[15]. *Komagataeibacter xylinus*, the most famous bacterium, has a high bacterial cellulose production capacity from a various carbon and nitrogen sources [13]-[16]. Various researchers have investigated the effects of varied factors (pH, temperature, bacterial species, carbon sources, media, etc.) on the BC production [9],[17]-[18]. In order to discover a new strain with increasing cellulose-producing capacity, researchers isolate bacteria from various sources such as fruits (grapes and rotten

*Corresponding author/Yazışılan Yazar

grapes, apple juice, rotten apples, melons, lemons, and papayas), flowers (passiflora), fermented foods (waste from vinegar fermentation, malt), and kombucha tea [19]-[26].

Bacterial polymers are natural products with commercial value. In particular, the capacity of BC to transform into products with high economic value has caused it to attract great interest in green and sustainable chemistry aspects, and it has become a hope for the development of new technologies. Because bacterial technology has many advantages including the ability to produce polymers in a short time, the purity of cellulose, its high-water holding capacity, and the ability to easily make new arrangements in the production process. On the other hand, although bacterial cellulose is considered an alternative to vegetable cellulose for environmental protection, its production cost is high. For this reason, recent research on the manufacture of BC is directed towards the production of cellulose in different microorganisms, the isolation of new microorganisms that produce cellulose from different environments, new regulations for improving the properties of microorganisms known to produce cellulose and increasing their production. In other words, selecting new species or isolates for efficient cellulose production by bacteria forms the basis of such studies. For this reason, many researchers isolate cellulose-producing bacteria from various sources and investigate their BC production capacities and properties.

The current research aimed to explore the production of BC using local isolate of *Komagataeibacter xylinus* S4, which was isolated from home-made grape vinegar [9]. For this purpose, the effects of growth media, carbon sources, pH, surface area, incubation temperature and period were investigated on manufacture. Obtained BC was characterized by FT-IR, scanning electron microscope (SEM), thermal analysis, and electrical conductivity measurements. In addition, cellulose acetate synthesis was also performed.

2 Material and Methods

2.1 Production and Purification of Bacterial Cellulose

Komagataeibacter xylinus S4 was used during the study [9]. BC was synthesized in standard HS [27], Yamanaka [28], and M1A05P5 media [29]. For determining the effects of carbon sources, xylose, arabinose, lactose, mannitol, fructose, and sucrose were added instead of glucose in HS broth. Also, temperature (20, 25, 30 and 35 °C), pH (3.5, 4.0, 4.5, 5.0, 5.5, 6.0, 6.5), incubation time (4, 7, 14, 21 days) and surface area to volume ratio (0.39 cm⁻¹, 0.66 cm⁻¹, 1.06 cm⁻¹) were tested. Harvested BC membrane contains protein, medium ingredients, and bacterial cells. To remove the unwanted contents of the native BC, it was kept at 0.1 M NaOH at 80 °C for 1 h. Then, BC was washed several times with deionized water. After processing, BC was lyophilized (Thermo Fisher ModulyoD Freeze Dryer and Telstar LyoQuest) and stored at -20 °C for analysis [30].

2.2 Water Holding Capacity (WHC)

The water holding capacity (WHC) is considered one of the most important physical characteristics of bacterial cellulose regarding the biomedical application of BC as wound dressing material. The WHC relates to the BC matrix's porosity and surface area. The high WHC of BC is due to its very porous and hydrophilic nature. In current study, the water holding capacity of the bacterial cellulose samples were the mass of water removed during drying divided by the dry weight of BC.

2.3 Acetylation of Bacterial Cellulose and Preparation of Cellulose Triacetate

Cellulose triacetate (CTA) is a cellulose derivative. CTA can be used in optical films such as protective films for LCD polarizing panels used in LCD TVs, notebook computers, and mobile phones. CTA was produced with some modifications with a described method by Braun et al. [31]. Uniform wetting of the cellulose was achieved by mixing 10 g of lyophilized BC in 50 mL of acetic acid solution containing 0.5 g of concentrated sulfuric acid in a 250 mL wide-necked flask. The flask was then allowed to stand for 1 hour at room temperature (RT). After the pretreatment, 50 mL of acetic anhydride (C₄H₆O₃) and 20 mL of acetic acid (CH₃COOH) solution were added into the flask and replaced in a water bath at 50 °C for 30 min. The solution after this time was called the primary solution. At the end of the period, 25 mL of CH₃COOH (80%) solution was added to the primary solution at 60 °C to break down the remaining acetic anhydride after the reaction, paying attention to avoid any precipitation at this stage. The obtained mixture was kept at 60 °C for 15 min and then poured into the beaker. After carefully adding 25 mL of distilled water, an additional 200 mL of distilled water was added to precipitate cellulose triacetate as a white powder. Obtained precipitate formed by the addition of distilled water was dried in an oven after filtering and washing. The obtained dry precipitate was dissolved in chloroform (CHCl₃) and poured into the petri dish. Chloroform was allowed to air-dry, and the obtained CTA was stored in a refrigerator for analysis.

Cellulose triacetate was characterized by determining the degree of substitution by saponification reaction [32]. The degree of substitution is the mean value of acetyl groups (CH₃CO) replacing hydroxyl groups (OH) in glycosidic units. For the saponification reaction, 0.1 g of cellulose triacetate was weighed, 5 mL of 0.25 M sodium hydroxide (NaOH) and 5 mL of ethanol (C₂H₅OH) were added to it, and it was kept at RT for 24 hours. After that, 10 mL of 0.25 M hydrochloric acid (HCl) was added to the mixture. After 30 min, titration with standard 0.25 M NaOH using phenolphthalein indicator was performed. Titration continued until the solution turned completely pink colour. As a result of titration, the percentage of acetyl groups in cellulose triacetate was calculated according to the equality given below.

$$AG\% = \frac{[V_{(NaOH)s} + V_{(NaOH)t}]XC_{NaOH} - V_{(HCl)s}C_{HCl}]43X100}{m_s} \quad (1)$$

In equation 1, the percentage of acetyl groups (AG%), NaOH volume added to the system (V_{(NaOH)s}), consumed NaOH volume (V_{(NaOH)t}), NaOH concentration (C_{NaOH}), the concentration of HCl (C_{HCl}), the molecular weight of the acetyl group (43), the weight of cellulose triacetate (m_s).

2.4 FT-IR Analysis

The Fourier Transformed Infrared Spectroscopy data of BC was recorded on a Bruker Vertex 70 V FT-IR spectrometer, with an attenuated total reflection unit between 400-4000 cm⁻¹ at RT.

2.5 Thermal Analysis

The chemical decomposition of BC was analyzed with Perkin Elmer Diamond branded instrument. Approximately 5 mg of BC was replaced in a ceramic pan. Temperature was increased at the speed of 20 °C/min from 50 °C to 600 °C under Nitrogen (N₂) gas with 200 mL/min flow rate. Differential scanning

calorimetry (DSC) analyses of BC were carried out using a Perkin Elmer Pyris 6 device. The sample was replaced in an aluminum pan and heated from 0 °C to 400 °C under nitrogen atmosphere (10 mL/min).

2.6 Scanning Electron Microscope (SEM)

For SEM analysis, BC-lyophilized was put on aluminum stamps and coated with gold-palladium approximately 2 min (PAU-ILTAM, Denizli).

2.7 Determination of Electrical Conductivity of Bacterial Cellulose

The electrical conductivity measurements of BC were performed between 27-137 °C. In order to provide electrical conduction of samples, conductive copper wires were tied to the samples with silver paste. BC with ohmic contacts was placed in a Janis cryostat, and the temperature was controlled with a LakeShore 331 temperature controller. KEITHLEY 2400 source measure unit was used as a current source in the system.

2.8 Statistical Analysis

The results of wet and dry weights, water contents and final pH analyses of BC were analyzed by using the SPSS package statistics program (TEAM EQX SPSS Statistics Version 16.0, 2007). In cases where the difference between changing environmental conditions and incubation times was significant, Duncan's test was applied to show the difference between different environmental conditions and incubation times and between each other. The standard deviations of the values were given in tables created. Statistically significant differences were determined at $p < 0.05$, while insignificant differences were determined at $p > 0.05$ level.

3 Results and Discussion

3.1 Production of Bacterial Cellulose

BC obtained from standard HS medium was characterized in our previous paper [9]. Our previous finding has shown that the wet and dry weights of bacterial cellulose were between 51.8-52.8 g and 0.43-0.735 g, respectively and, the morphology of cellulose layer was observed as a dense nanofiber network. The weight of BC also decreased with increasing temperature between 50 °C and 150 °C, and the degradation step observed between 215 °C and 228 °C. Moreover, the antibiofilm and antibacterial effects of unmodified BC have also been reported for the first time [9]. The potential values of local isolates and their products have a considerable industrial concern. Therefore, the production of bacterial cellulose from *K. xylinus* S4-local isolate was shown in detail in this study. Different carbon sources (xylose, arabinose, lactose, mannitol, fructose, sucrose), temperature, pH, and surface area/volume ratio, which affect the production of BC, were investigated.

Wet weight results of BC were consistent with the dry weight results. In addition, when the results in Table 1 were examined, considering the carbon sources, the amount of BC from carbon sources was achieved in the order of sucrose > fructose > mannitol > xylose > arabinose > lactose. Mannitol (0.19g/L), fructose (0.233g/L), and sucrose (0.273g/L) showed significant increases in BC production among all sources. Especially, the yields of BC in fructose and sucrose medium seem to be relatively higher. The lowest BC yield was achieved in lactose (0.018g/L), arabinose (0.026g/L), and xylose (0.095g/L) medium. In other words, while sucrose, fructose, and mannitol

positively affected cellulose production, xylose, arabinose, and lactose did not contribute the manufacture of BC (Table 1).

Table 1. The wet and dry weights of BC from *Komagataeibacter xylinus* S4 (T: 30 °C; pH: 6.0; incubation period: 4 days, HS medium containing different carbon sources).

Carbon sources	Wet Weight (g/L)	Dry Weight (g/L)	pH _f	WHC (g-water/g-dry BC)
Xylose	17.25±0.1	0.095±0.00	4.89±0.	181±0.5
Arabinos	8.88±0.08	0.026±0.00	5.22±0.	341±1.5
Lactose	8.78±0.02	0.018±0.00	5.57±0.	487±1.0
Mannitol	22.60±0.1	0.190±0.00	5.54±0.	118±1.0
Fructose	33.10±1.0	0.233±0.00	5.35±0.	141±2.5
Sucrose	32.41±0.4	0.273±0.00	5.45±0.	118±4.5

The differences between the wet and dry weights, pH final and water content of the ones (a,b,c,d,e) shown with different lowercase letters at each carbon source are important.

Nguyen and co-authors reported that *G. xylinus* isolated from Kombucha tea produced the highest yield with mannitol as the carbon source [26]. Tonouchi et al. [33] claimed that fructose as a carbon source increased the manufacture of BC. A similar study showed that the optimum production of BC with pH resistant *Komagataeibacter medellinensis* was achieved in the medium of glucose > sucrose > fructose [34]. Hungund and Gupta [22] also examined the effects of carbon sources including glucose, fructose, lactose, sucrose, mannitol, maltose, and inositol for cellulose production and obtained the highest BC yield in fructose medium. According to Mikkelsen et al. [35], *G. xylinus* ATCC 53524 produced the highest BC production under HS broth with sucrose and glucose after 96 hours. Sucrose was the favoured carbon source for *Acetobacter* sp. 4B-2 [36]. According to the literature review, it can be understood that the types of bacteria, nutrients, or carbon sources are the main reasons for the differences in cellulose production. Therefore, optimization studies should be carried out in detail according to each bacterial isolate. When the obtained data from our study and the literature data were compared, it was determined that *K. xylinus* S4 strain preferred the environment of glucose, sucrose, and fructose for BC synthesis.

This study also showed the influences of Yamanaka and M1A05P5 media on BC production. Our findings show that while *K. xylinus* S4 did not produce cellulose in Yamanaka medium, the M1A05P5 medium had BC production clearly different from HS medium. In other words, M1A05P5 medium gave higher BC production than HS medium containing different carbon sources, indicating that M1A05P5 on BC production was more effective than *K. xylinus* S4. As can be seen from Table 2-3, three different combinations of surface area/volume ratio (A1: 0.39 cm⁻¹, A2: 0.66 cm⁻¹, A3: 1.06 cm⁻¹) and temperature (25, 30, and 35 °C) were examined to increase BC production in M1A05P5 medium.

Combined with A3 (1.06 cm⁻¹) and 30 °C temperature, the production of BC was higher than the other combinations (Table 2 and 3). The A3 and 30 °C temperature condition (Table 4) was tested in 7, 14, and 21 incubation days at pH 3.5 and 6.5 values, and it was clearly verified that all combinations had high BC production in incubation periods. In particular, the incubation in 14 days showed a significant increase in BC production at pH 6.5. In summary, the environmental conditions for the best bacterial cellulose production were

determined as M1A05P5 condition at 30°C under pH 6.5 in 14 days, with 1.06 cm⁻¹ (surface area/volume ratio). The wet weight was 463.80 g/L, and the dry weight was 2.36 g/L. Coban and Biyik found that BC production by *Acetobacter lovaniensis* HBB5 was 0.04 g/L after 7 days in Hestrin-Schramm (HS) medium that contained 2% (w/v) glucose and 0.5% yeast extract [37].

Table 2. BC production by *Komagataeibacter xylinus* S4 in M1A05P5 medium (incubation period: 4 days, pH: 3.5).

Surface area/Volume ratio	T (°C)	Wet Weight (g/L)	Dry Weight (g/L)	WHC (g-water/g-dry BC)
0.39 cm ⁻¹	20	23.27±0.84 Aa	0.20±0.01 Aa	115±4.00 Ab
	25	66.02±0.12 Ab	0.31±0.05 Ab	212±8.00 Cb
	30	136.88±0.8 6Ac	0.63±0.03 Ac	216±7.00 Cb
	35	154.86±0.5 4Ad	0.63±0.05 Ad	245±4.00 Bb
0.66 cm ⁻¹	20	60.31±0.46 Ba	0.32±0.02 Ba	187±3.00 Ab
	25	117.91±2.0 9Bb	0.54±0.07 Bb	217±9.00 Cb
	30	210.78±3.4 0Bc	1.04±0.03 Bc	202±8.00 Cb
	35	193.65±0.7 8Bd	1.01±0.02 Bd	191±5.00 Bb
1.06 cm ⁻¹	20	93.05±0.26 Ca	0.67±0.01 Ca	138±2.00 Aa
	25	154.08±0.2 0Cb	0.81±0.04 Cb	189±5.00 Ca
	30	228.58±0.9 0Cc	1.19±0.09 Cc	191±14.0 0Ca
	35	96.70±0.20 Cd	0.72±0.02 Cd	133±1.00 Ba

The differences between the wet and dry weights and the water content of those shown with different capital letters (A,B,C) in each surface area/volume ratio were important. The differences between the wet and dry weights and the water content of the ones (a,b,c,d) shown with different lowercase letters at each temperature were important.

Additionally, Cakar et al. [29] stated that the yield of BC decreased on the first day of incubation at pH 6.0 ≥ values in M1A05P5 medium. Unlike the findings of Cakar and co-authors, *K. xylinus* S4 strain continued producing cellulose at pH 6.5 and it was observed that it produced the highest cellulose yield (2.36 g/L) in 14 days of incubation time. According to Ishihara et al. [38], *Acetobacter xylinus* IFO 15606 produced cellulose at a yield exceeding 0.3 g per 100 ml with pH control. Similarly, our isolate S4 was a strain that can compete with the producers in the literature. In other words, *K. xylinus* S4 strain was at least as good a producer.

Table 3. BC production from *Komagataeibacter xylinus* S4 in M1A05P5 medium (incubation period: 4 days, pH: 6.5).

Surface area/Volume ratio	T (°C)	Wet Weight (g/L)	Dry Weight (g/L)	WHC (g-water/g-dry BC)
0.39 cm ⁻¹	20	33.04±0.08 Aa	0.124±0.0 1Aa	265±2.25Bc
	25	42.39±0.18 Ab	0.154±0.0 1Ab	274±2.24Dc
	30	86.35±0.34 Ac	0.273±0.0 1Ac	315±1.74Cc
	35	146.92±0.1 1Ad	0.637±0.0 1Ad	230±0.60Ac
0.66 cm ⁻¹	20	51.27±0.08 Ba	0.217±0.0 1Ba	235±1.21Bb
	25	128.01±0.2 0Bb	0.566±0.0 1Bb	225±3.79Db
	30	209.60±0.4 0Bc	0.970±0.0 1Bc	215±4.71Cb
	35	209.51±0.3 1Bd	0.905±0.0 1Bd	231±1.84Ab
1.06 cm ⁻¹	20	102.90±0.0 7Ca	0.501±0.0 2Ca	204±3.07Ba
	25	175.18±0.3 8Cb	0.771±0.0 2Cb	226±2.43Da
	30	253.34±0.4 3Cc	1.358±0.0 2Cc	186±2.88Ca
	35	263.82±0.1 2Cd	1.280±0.0 5Cd	205±1.49Aa

The differences between the wet and dry weights and the water content of those shown with different capital letters (A,B,C) in each surface area/volume ratio were important. The differences between the wet and dry weights and the water content of the ones (a,b,c,d) shown with different lowercase letters at each temperature were important.

Glucose dehydrogenases cause an increase in the acidity of the media and reduce bacterial cellulose production in glucose-containing media [39]-[41]. Seto et al. [42] and Masaoka et al. [43] also support this idea. In the previous studies, high bacterial cellulose production was observed in bacterial media with low glucose dehydrogenase activity and low bacterial cellulose production was observed in bacterial media with high glucose dehydrogenase activity. Nevertheless, *K. xylinus* S4 used in our study showed high cellulose production yields even at near or neutral pH conditions. Therefore, it was considered that the *K. xylinus* S4 had low glucose dehydrogenase activity.

Table 4. BC production by *Komagataeibacter xylinus* S4 in the combination of surface area/volume ratio and temperature (1.06 cm⁻¹, 30°C).

	Wet Weight (g/L)	Dry Weight (g/L)	pH _f	WHC (g·water/g·dry BC)
pHi: 3.5				
7th day	117.09±0.22 _a	1.145±0.01 _a	3.11±0.02 _a	101±4.00 _a
14th day	207.85±0.32 _c	1.161±0.05 _a	3.20±0.03 _b	178±1.55 _c
21st day	204.10±0.23 _b	1.303±0.01 _b	3.12±0.03 _a	156±2.61 _b
pHi: 6.5				
7th day	274.61±0.41 _a	1.535±0.03 _a	5.80±0.08 _a	178±2.42 _a
14th day	463.80±0.43 _c	2.364±0.05 _c	8.23±0.03 _b	195±5.08 _c
21st day	335.60±0.64 _b	1.895±0.01 _b	8.23±0.04 _b	176±4.81 _b

The differences between the wet and dry weights and the water content of the ones (a,b,c) shown with different lowercase letters at each day are important.

The water holding capacities of different BCs produced in different media were shown in the tables. According to the results, it was seen that the WHC values of the produced BC were quite high (101±4.00 g/g to 487±1.00 g/g). It was noteworthy that the WHC values of our BCs were generally higher than the values of similar studies in the literature [12], [44]-[45].

3.2 SEM Analysis of Bacterial Cellulose

The scanning electron microscope photos of the synthesized BC with *K. xylinus* S4 under different conditions were also investigated (Figures 1 and 2). Although there were similarities in the morphological structures of bacterial cellulose, the fibril thicknesses were not identical. The thickness of the fibrils was found to be between 29.71nm and 102.3nm. Moreover, the fibril structure of cellulose obtained from all conditions (except mannitol) was thin.

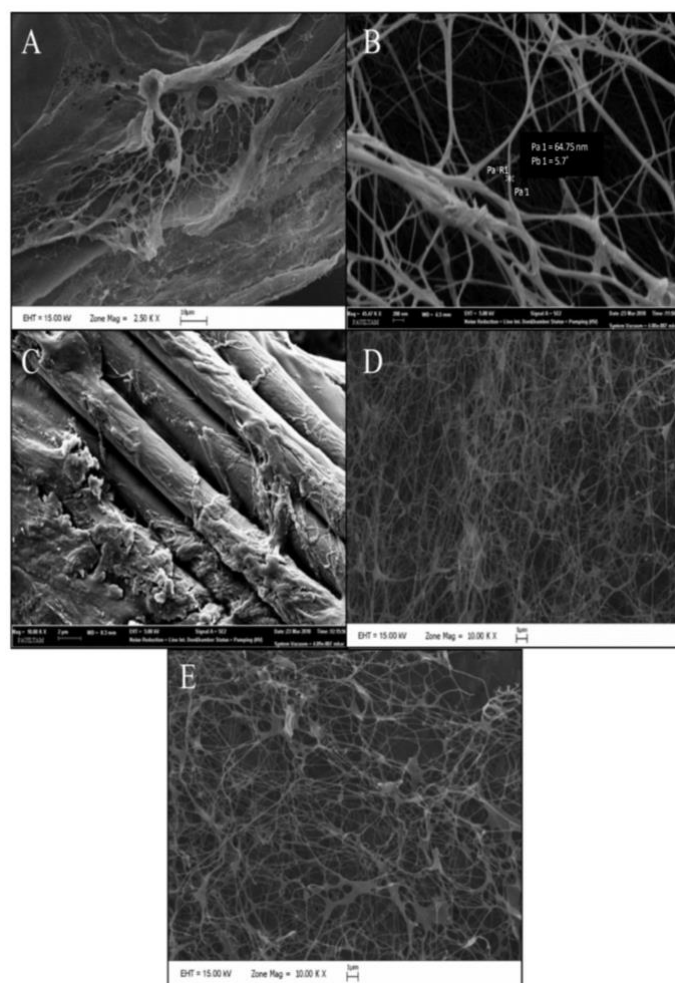


Figure 1. SEM images of BC obtained from *Komagataeibacter xylinus* S4. **A:** Main source, **B:** Lactose **C:** Mannitol **D:** Fructose **E:** Sucrose.

In addition to that, fibril distribution and interfacial adhesion of cellulose in each medium were also different. It was observed that cellulose obtained from all media (except lactose) had a more stable and compact network structure. In other words, the less fibrillary structure was imaged in the medium containing lactose, and the fibril diameter was found to be 64.75nm. We noticed the uniaxial oriented cellulose bands and strong interfacial adhesion of fibers in mannitol medium (Figure 2). In addition, cellulose from M1A05P5 medium was observed to be in dense fibril bundles and their diameters were between 34.87-45.97nm under pH:3.5 and 29.71-102.3 nm under pH:6.5. BC is defined as a reticular substance composed of ultra-fine cellulose fibrils and, various factors including nutrients, growth conditions, and bacterial species affect both the production of BC and its fibril structure [17], [46].

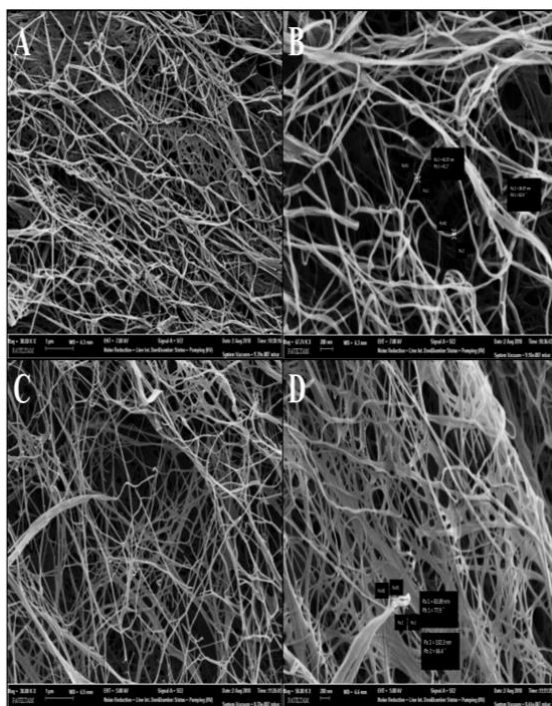


Figure 2. SEM pictures of the produced BC with *Komagataeibacter xylinus* S4 under M1A05P5 medium at various pH values. A-B: pH 3.5, C and D: pH 6.5.


For example, according to Jung et al. [46], BC from *Acetobacter* sp. was a reticulated structure with ultrafine fibrils and its diameter was approximately 65-80 nm and 75-90 nm in glycerol and glucose medium, respectively. However, Vazquez et al. [47] showed that cellulose obtained from modified HS, glycerol, and molasses had a fibrillary network structure and the fibril diameter varied from 35 to 70 nm. In another study, it was reported that the diameter of *Acetobacter xylinum* cellulosic fibrils ranged from 128-207 nm and BC fibrils were the same as fibrils in pure microcrystalline cellulose [48]. In a study investigating the influence of ascorbic acid on the production of BC with *Komagataeibacter xylinus*, it was determined that the size of BC nano-fibrils was found to be in the range of 45-55 nm by SEM analyzes [13].

3.3 Fourier Transform Infrared (FT-IR) Spectra Analysis

Fourier transform infrared spectra results of the obtained BCs were recorded on using an ATR-FT-IR spectrophotometer (Bruker Vertex 70 V, Germany) between 400 and 4000 cm^{-1} wavelengths (Figure 3). These spectra were used to investigate vibrational bands of the functional groups of BC produced under various carbon sources and culture media.

The following determinations were determined to analyze FTIR spectra of BC. The broad bands that appeared at 3300 cm^{-1} were assigned to -OH stretching vibrations of samples due to the formation of hydrogen bonds. The peak at 2950 cm^{-1} showed C-H stretching. This peak was ascribed to the C-H stretching vibrations of -CH₂ and -CH₃ groups. The peaks in the wavenumber range of 1750-1400 were associated with protein, lipid, and nucleic acid. The vibration bands at 1426 and 1315 cm^{-1} were attributed to the bending vibrations of CH₂ and C-H groups of polysaccharides. The peak of C-O stretching vibration was located at 1159 cm^{-1} . The bands in the range of 1000-1200 cm^{-1} could be associated with the vibrations of C-O and C-O-C functional groups in pyranose ring. The further

vibration peaks seen for BC (Figure 3A-B) were fixed to -C-H out-of-plane bending (896 cm^{-1}) and -OH out-of-plane bending (666-619 cm^{-1}) vibrations. Obtained vibration bands from FT-IR spectra proved the successful synthesis of BC. Fig. 3C shows the difference between FT-IR spectra of BC from glucose and CTA produced from BC. According to Fig. 3C, the intensity vibration band appeared around 1737 cm^{-1} representing the carbonyl group of CTA. -OH stretching vibration of CTA was disappeared around 3360 cm^{-1} . The disappearance of -OH stretching vibration and the existence of carbonyl group in FT-IR spectra proved the cellulose triacetate formation from BC. In other words, FT-IR spectra evidenced the production of BC and CTA. In addition, the percentage of acetyl groups of cellulose triacetates synthesized from bacterial cellulose was calculated as 44.9% by using equation 1. The cellulose triacetate has a degree of hydroxyl substitution 2.98. The degree of substitution value was calculated using the acetyl group value [49].

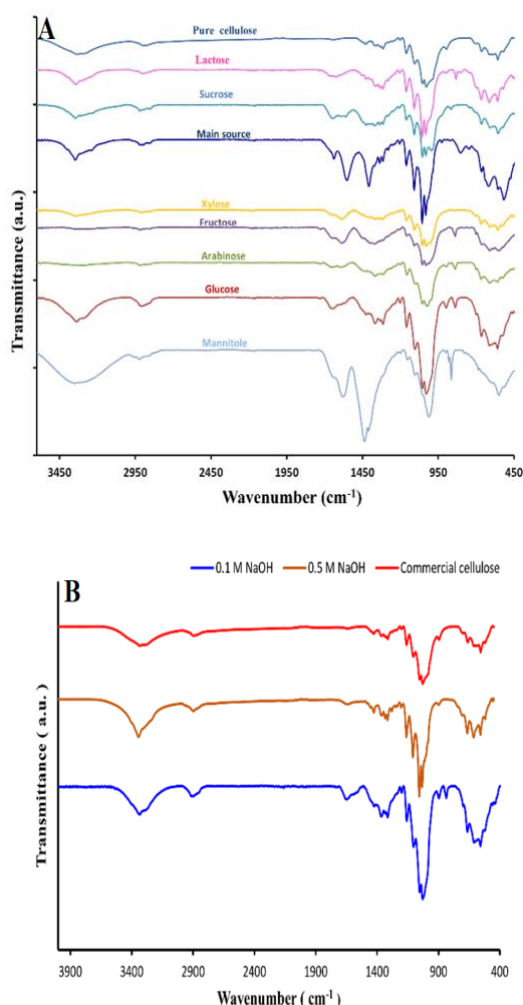

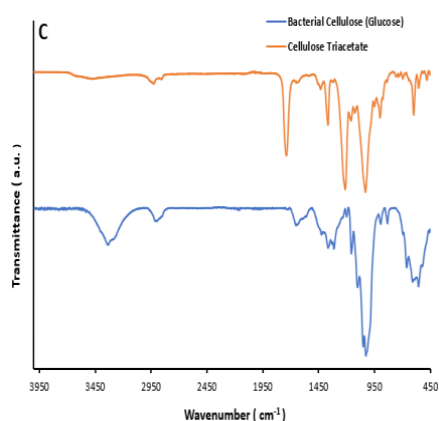


Figure 3. FT-IR spectra of BC samples and Cellulose triacetate synthesized from BC. **A:** Monosaccharides and Disaccharides as carbon source, **B:** The effect of different concentrations of NaOH in the workup procedure, **C:** Cellulose triacetate synthesized from BC.

3.4. Thermal Analysis (TG-DTG)

Thermal degradation of bacterial cellulose was characterized with Perkin-Elmer Diamond brand instrument. All analyzes were performed under N₂ atmosphere with a 200 mL/min flow rate, using a ceramic sample pan at temperatures between 50 °C and 600 °C with 20 °C/min heating rate. Approximately, 5 mg of BC was used in the analyses.

Thermogravimetric analysis (TG) of bacterial cellulose was accomplished to better understand the thermal degradation behaviors of BC during the thermochemical transformations. Because the results of TG analysis depend on many parameters, including sample geometry, sample mass, and heating rate. These parameters should be constant during the analysis process. The weight loss of BC obtained from different carbon sources was determined by increasing temperature. Thermogravimetric analysis (TG) and Differential Thermogravimetric (DTG) curves were respectively shown in Figure 4A and Figure 4B.

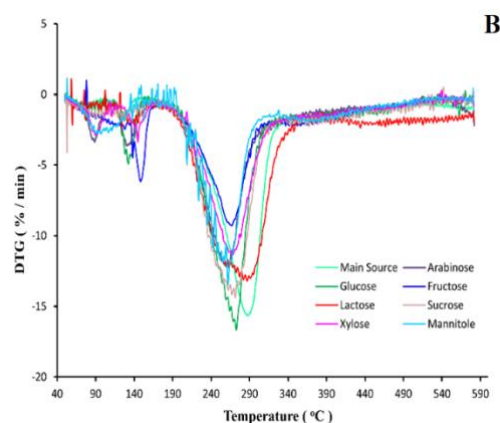
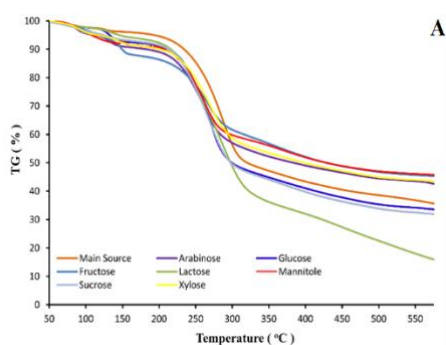


Figure 4. TG and DTG curves of BCs of *Komagataeibacter xylinus* S4 grown in HS medium with the addition of different carbon sources; A: TGA curves, B: DTG curves.

In addition, some results such as the starting degradation, the final degradation temperature, the maximum degradation temperature, and the pyrolysis residue value after heating to 550 °C obtained from the TG and DTG curves were summarized in Table 5.

Table 5. The thermal decomposition temperatures of BC from *K. xylinus* S4 grown under HS medium with different carbon sources.

Carbon Source	T _{onset} (°C)	T _{offset} (°C)	T _{max} (°C)	Residue at 550 °C (wt %)
Main Source	214.49	325.84	287.46	36.80
Fructose	227.91	299.92	266.76	45.71
Xylose	227.11	290.72	268.25	43.97
Sucrose	223.97	294.16	271.36	32.50
Lactose	221.32	318.48	286.64	18.02
Arabinose	216.9	279.22	259.72	43.53
Mannitol	221.74	276.33	261.99	46.14
Glucose*	227.23	288.10	272.72	34.19

*Standart HS medium containing glucose

The thermal degradation behavior of BC consists of weight loss steps including dehydration and depolymerization of the polymer network [50]. First weight loss occurred in the dehydration step, which is related to evaporation of water molecules attached to cellulose fibrils, which occurs between the temperatures of 50-150 °C. As can be seen in Figure 4, our results were also compatible with the literature [47], [51]-[53]. Cellulose is a polymer with moderate thermal stability and degrades rapidly at temperatures between 250 °C to 350 °C [54]. In our study, the main degradation step with high percent weight loss appeared between 215 °C and 290 °C for all samples. It was seen that the second degradation step initialized between 215 °C and 228 °C temperatures.

DTG analysis also confirmed that the maximum weight loss rate was between 260 °C-288 °C. The maximum decomposition temperatures of BC from various carbon sources were observed between 277 °C and 326 °C (Table 5). These thermal values were somewhat lower with respect to the similar works [47], [53], [55]-[57]. It is known that the thermal degradation behavior of cellulose can be altered by some structural parameters including the cellulose fibres orientation, crystallinity, and molecular weight [53]. In addition to these structural parameters, thermal degradation behavior could be affected by many factors including the cleaning procedure in

the purification step, the preparation of sample for thermal analysis, and the morphology and size of the sample [58]. As stated in the information mentioned above, this difference could be due to the purification step of the BC. After changing the work-up procedure of BC, the observed degradation steps of BC were consistent with the results in the literature. After heating to 550 °C, the high pyrolysis residues of BC also supported the accuracy of this evaluation.

TG and DTG curves of BC samples obtained at various pH values in M1A05P5 medium of *K. xylinus* S4 bacteria and BC-based cellulose acetate obtained from these samples were given in Figure 5. Also, the detailed results obtained by thermogravimetric analysis of bacterial cellulose produced in Hestrin-Schramm medium with different carbon sources and in M1A05P5 medium with different pH values were shown in Table 5. And finally, the detailed results for thermogravimetric analysis of cellulose acetate in M1A05P5 medium were presented in Table 6. It was determined from the TG and DTG curves of BC-based cellulose acetate that the initial temperature of degradation was 332.52 °C, the final temperature of degradation was 395.02 °C and the maximum decomposition temperature was 367.11 °C. As seen in Figure 5, the decomposition step took place in a single step, as the BC samples were dried before thermal analysis.

Table 6. Thermal properties of BC obtained at different pH values in M1A05P5 medium of *K. xylinus* S4 bacteria and BC-based cellulose triacetate obtained from those samples.

Carbon Source	T _{onset} (°C)	T _{offset} (°C)	T _{max} (°C)	Residue at 550 °C (wt%)
M1A05P5, pH 3.5	308.85	379.12	356.67	12.42
M1A05P5, pH 6.5	301.27	375.38	349.15	2.89
Cellulose Triacetate	332.52	395.02	367.11	15.36

The decomposition phase of BC obtained in M1A05P5 medium started between 301.27 °C and 308.85 °C and was completed between 375.38 °C and 379.12 °C. After the BC and BC-based cellulose acetate were heated to 550 °C, the remaining pyrolysis residue values varied between 2.89 to 15.36 % (Figure 5).

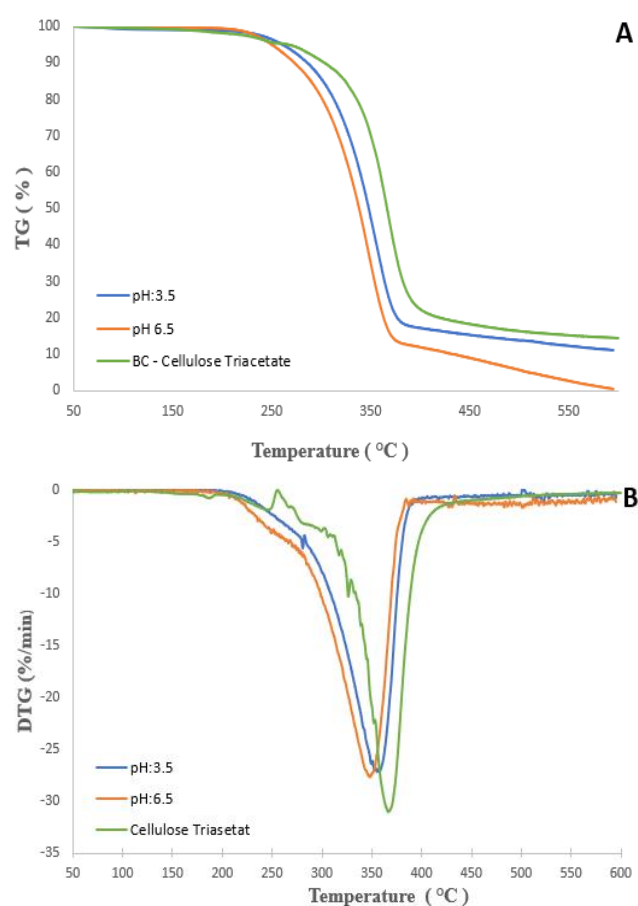


Figure 5. Thermogravimetric analysis curves of BC samples of *Komagataeibacter xylinus* S4 grown in M1A05P5 medium at different pH values and BC-based cellulose acetate obtained from those samples; A: TG curves, B: DTG curves.

Thermal analysis results also confirmed the synthesis of cellulose triacetate (CTA). Cellulose triacetate showed different thermal behavior during the analysis. The pyrolysis rate of BC was 2.89-12% at 550 °C while the pyrolysis rate of cellulose triacetate was 15.36-369 °C. According to thermal analysis data, CTA was more resistant to high temperatures than BC. Moreover, the mass loss of CTA was less than that of BC. In the current study, acetylation of BC was studied for 24 h. According to Barud et al. [53], there is a significant relationship between acetylation time and mass loss in thermal analysis. They studied three different acetylation duration 1 hour, 6 hours, and 24 hours and reported increased crystallinity and thermal stability at the 24 hours of acetylation duration.

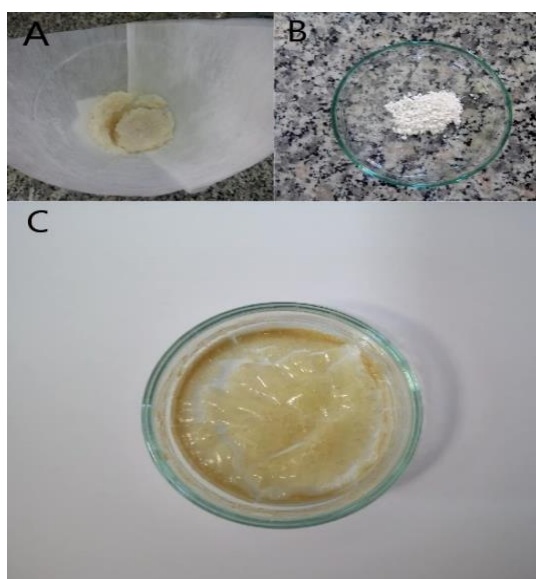


Figure 6. The photography of cellulose acetate. *Komagataeibacter xylinus* S4 was grown in M1A05P5 medium. After filtration (A), Cellulose triacetate in powder (B) and dry forms (C).

A high degree of purity is mainly looked for in the synthesis of cellulose derivatives. For example, CTA is one of the most essential cellulose esters due to its low cost, non-toxic and non-flammable, renewable, and biodegradable properties. Cellulose triacetate can be synthesized through the reaction between cellulose with acetic anhydride and acetic acid in the presence of sulfuric acid [59]. CTA has been synthesized from bacterial cellulose by some scientists, and its acetylation methods, physical and thermal properties have also been studied. It has been determined that bacterial cellulose can be an alternative to plant-derived cellulose in the synthesis of cellulose triacetate [60]-[63]. The cellulose acetate synthesis steps were illustrated in Figure 6 and SEM images of cellulose triacetate were presented in Figure 7.

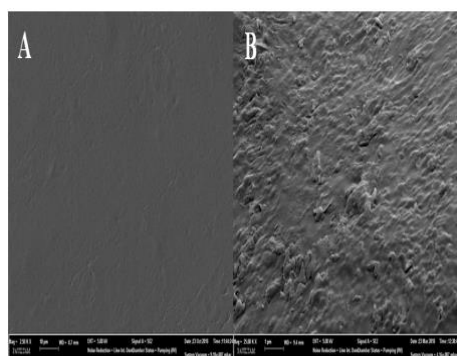


Figure 7. SEM images of CTA, A:250 KX, B:2500 KX

3.4. Electrical conductivity of BC

Today, biopolymers modified with organic or inorganic components are promising composites for organic electronic material production and medicine. Sensors, flexible electrodes, conductive flexible screen applications with good mechanical properties, polymeric films, electrolyte gels, capacitors, carbon nanotubes, or new potential application areas including tissue engineering due to their cell regeneration properties are also important to study BC-based materials [64]-[71]. For this purpose, the electrical conductivity measurements of three BC

samples were accomplished at 27-137 °C. Figure 8 shows the variation of conductivity with inverse temperature. It was observed that the conductivity increased exponentially with increasing temperature. Thus, it was concluded that BC exhibited semiconducting behaviors. The room temperature electrical resistivity values were measured to be $1.23 \times 10^5 \text{ ohm-cm}$, $1.03 \times 10^6 \text{ ohm-cm}$ and $2.80 \times 10^6 \text{ ohm-cm}$ for BC-1, BC-2 and BC-3, respectively.

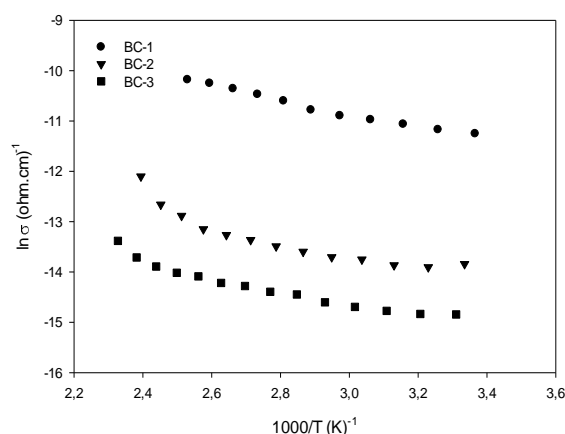


Figure 8. Temperature dependence of electrical conductivity of BCs (BC-1; bacterial celluloses obtained from HS medium, BC-2; pH: 3.5, BC-3; pH: 6.5).

The temperature dependence for the electrical conduction in the entire temperature range was analyzed by using the conductivity expression.

$$\sigma = \sigma_0 e^{-\frac{E_a}{kT}} \quad (2)$$

In equation 2, σ_0 is a constant, E_a is the thermal activation energy for conductivity, and k is the Boltzmann constant [70]. The plot of $\ln \sigma$ versus $1000/T$ in Figure 8 indicates that the slope of the linear region gives the activation energy. According to Figure 8, there was only one activation energy owing to a single slope region. In the temperature range of 27-137 °C, the activation energies of samples were calculated as 123 meV, 115 meV and 103 meV for BC-1, BC-2 and BC-3 respectively.

4 Conclusions

The need for increasing cellulose demand due to the increasing world population shows that alternative cellulose production is necessary. Especially, the decrease in vegetable sources shows that it would be wise to discover alternative sources for cellulose production. Undoubtedly, cellulose produced from bacteria is not yet cheap and economical. However, human beings know that they must use the world's resources rationally. In the current study, bacterial cellulose from *Komagataeibacter xylinus* S4 was characterized by SEM, FT-IR, and thermal analysis and, its electrical conductivity was also investigated. According to SEM analyses, there were unidirectional cellulose fibers and the interfacial adhesion between fibrils was detected in mannitol. The fibrils of bacterial cellulose obtained from other carbon sources and M1A05P5 medium also had a network-like appearance. In addition, BC showed semiconductor property. Improving the conductivity properties of BC can be used in various engineering branches. Last of all, a detailed investigation of bacterial cellulose-based cellulose triacetate will excite for future studies as an essential natural material.

5 Acknowledgments

The authors thank to Pamukkale University Scientific Research Projects Coordinator (Project Number 2017FEBE018) for financial supporting and Dr. Aysel Yeşilyurt Er (Çal Vocational High School, Pamukkale University) for the grape vinegar.

6 Author Contribution Statements

In this study, the first author has made contribution to the concepts of literature review, research planning, design and direction of experimental studies, evaluation of results, supply of resources and materials, and writing of the article.

In the study, the last author has made contribution to the concepts of literature review, design and direction of experimental studies, evaluation of results, and writing of the article.

In the study, other authors have made contributions to the concepts of literature review, experiments and analysis, spelling, creation of graphics and tables from the results of experiments and analysis and writing of the article.

7 Conflict of Interest

The authors declare no competing interests. All co-authors have seen and agree with the contents of the manuscript.

8 References

- [1] Ang, JF. "Water-retention capacity and viscosity effect of powdered cellulose". *Journal of Food Science*, 56, 1682-1684, 1991.
- [2] Heinamaki JT, Lehtola VM, Nikupaavo P, Yliruusi J. K. "Mechanical and moisture permeability properties of aqueous-based hydroxypropyl methylcellulose coating systems plasticized with polyethylene glycol". *International Journal of Pharmaceutics*, 112(2), 191-196, 1994.
- [3] Ren X, Kocer HB, Worley S, Broughton T, Huang V. "Rechargeable biocidal cellulose: synthesis and application of 3-(2,3-dihydroxypropyl)-5,5-dimethylimidazolidine-2,4-dione". *Carbohydrate Polymers*, 75, 683-687, 2009.
- [4] Zhang T, Zhou P, Zhan Y, Shi X, Lin J, Du Y, Li X, Deng H. "Pectin/lysozyme bilayers layer-by-layer eposited cellulose nanofibrous mats for antibacterial application". *Carbohydrate Polymers*, 117, 687-693, 2015.
- [5] Wang J, Tavakoli J, Tang Y. "Bacterial cellulose production, properties and applications with different culture methods—A review". *Carbohydrate Polymers*, 219, 63-76, 2019.
- [6] Trovatti E, Oliveira L, Freire CSR, Silvestre AJD, Neto CP, Pinto JJCC, Gandini A. "Novel Bacterial Cellulose-Acrylic Resin Nanocomposites". *Composites Science and Technology*, 70, 1148-1153, 2010.
- [7] Keshk SMAS. "Vitamin C enhances bacterial cellulose production in *Gluconacetobacter xylinus*". *Carbohydrate Polymers*, 99, 98-100, 2014.
- [8] Rozenberga L, Skute M, Belkova L, Sable I, Vikele L, Semjonovs P, Sakab M, Ruklisha M, Paegle L. "Characterisation of films and nanopaper obtained from cellulose synthesised by acetic acid bacteria". *Carbohydrate Polymers*, 144, 33-40, 2016.
- [9] Top B, Uguzdogan E, Dogan NM, Arslan S, Bozbeyoglu NN, Kabalay B. "Production and characterization of bacterial cellulose from *Komagataeibacter xylinus* isolated from home-

made Turkish wine vinegar". *Cellulose Chemistry and Technology*, 55 (3-4), 243-254, 2021.

- [10] Yano H, Sugiyama J, Nakagaito AN, Nogi M, Matsuda T, Hikita M, Handa H. "Optically transparent composites reinforced with networks of bacterial nanofibers". *Advanced Materials*, 17, 153-155, 2005.

- [11] Dahman Y, Jayasuriya KE, Kalis M. "Potential of Biocellulose Nanofibers Production from Agricultural Renewable Resources: Preliminary Study". *Applied Biochemistry and Biotechnology*, 162, 1647-1659, 2010.

- [12] Ul-Islam M, Khan T, Park JK. "Water holding and release properties of bacterial cellulose obtained by in situ and ex situ modification". *Carbohydrate Polymers*, 88, 596-603, 2012.

- [13] Raiszadeh-Jahromi Y, Rezazadeh-Bari M, Almasi H, Amir S. "Optimization of bacterial cellulose production by *Komagataeibacter xylinus* PTCC 1734 in a low-cost medium using optimal combined design". *Journal of Food Science and Technology*, 57, 2524-2533, 2020.

- [14] Lisdiyanti P, Navarro RR, Uchimura T, Komagata K. "Reclassification of *Gluconacetobacter hansenii* strains and proposals of *Gluconacetobacter saccharivorans* sp. nov. and *Gluconacetobacter nataicola* sp. nov". *International Journal of Systematic and Evolutionary Microbiology*, 56, 2101-2111, 2006.

- [15] Rangaswamy BE, Vanitha KP, Hungund BS. "Microbial Cellulose Production from Bacteria Isolated from Rotten Fruit". *International Journal of Polymer Science*, 280784, 2015.

- [16] Jahan F, Kumar V, Saxena RKK. "Distillery effluent as a potential medium for bacterial cellulose production: A biopolymer of great commercial importance". *Bioresource Technology*, 250, 922-926, 2018.

- [17] Mohammadkazemi F, Azin M, Ashori A. "Production of bacterial cellulose using different carbon sources and culture media". *Carbohydrate Polymers*, 117, 518-523, 2015.

- [18] Pacheco G, Nogueira CR, Meneguim AB, Trovatti E, Silva MCC, Machado RTA, Ribeiro SJL, da Silva Filho EC, Barud HdS. "Development and characterization of bacterial cellulose produced by cashew tree residues as alternative carbon source". *Industrial Crops and Products*, 107, 13-19, 2017.

- [19] Kojima Y, Tonouchi N, Tsuchida T, Yoshinaga F, Yamada Y. "The characterization of acetic acid bacteria efficiently producing bacterial cellulose from sucrose: The proposal of *Acetobacter xylinum* subsp. *nonacetoxidans* subsp. nov". *Bioscience, Biotechnology, and Biochemistry*, 62, 185-187, 1998.

- [20] Son C, Chung S, Lee J, Kim S. "Isolation and cultivation characteristics of *Acetobacter xylinum* KJ-1 producing bacterial cellulose in shaking cultures". *Journal of Microbiology and Biotechnology*, 12, 722-728, 2002.

- [21] Dellaglio F, Cleenwerck I, Felis GE, Engelbeen K, Janssens D, Marzotto M. "Description of *Gluconacetobacter swingsii* sp. nov. and *Gluconacetobacter rhaeticus* sp. nov., isolated from Italian apple fruit". *International Journal of Systematic and Evolutionary Microbiology*, 55, 2365-2370, 2005.

- [22] Hungund BS, Gupta SG. "Production of bacterial cellulose from *Enterobacter amnigenus* GH-1 isolated from rotten apple". *World Journal of Microbiology and Biotechnology*, 26, 1823-1828, 2010.

- [23] Suwanposri A, Yukphan P, Yamada Y, Ochaikul D. "Identification and biocellulose production of

- Gluconacetobacter strains isolated from tropical fruits in Thailand". *Maejo International Journal of Science and Technology*, 7, 70-82, 2013.
- [24] Aydin YA, Aksoy ND. "Isolation and characterization of an efficient bacterial cellulose producer strain in agitated culture: Gluconacetobacter hansenii P2A". *Applied Microbiology and Biotechnology*, 98, 1065-1075, 2014.
- [25] Jia S, Ou H, Chen G, Choi D, Cho K, Okabe M, Cha WS. "Cellulose production from Gluconobacter oxydans TQ-B2". *Biotechnology and Bioprocess Engineering*, 9, 166-170, 2004.
- [26] Nguyen VT, Flanagan B, Gidley MJ, Dykes GA. "Characterization of cellulose production by a Gluconacetobacter xylinus strain from Kombucha". *Current Microbiology*, 57, 449-453, 2008.
- [27] Hestrin S, Schramm M. "Synthesis of cellulose by Acetobacter xylinum: 2. Preparation of freeze-dried cells capable of polymerizing glucose to cellulose". *Biochemical Journal*, 58(2), 345-352, 1954.
- [28] Yamanaka S, Watanabe K, Kitamura N, Iguchi M, Mitsunashi S, Nishi Y, Uryu M. "The structure and mechanical properties of sheets prepared from bacterial cellulose". *Journal of Materials Science*, 24, 3141-3145, 1989.
- [29] Çakar F, Katı A, Özer I, Demirbağ DD, Şahin F, Aytekin AÖ. "Newly developed medium and strategy for bacterial cellulose production" *Biochemical Engineering Journal*, 92, 35-40, 2014.
- [30] McKenna BA, Mikkelsen D, Wehr JB, Gidley MJ, Menzies NW. "Mechanical and Structural Properties of Native and Alkali-Treated Bacterial Cellulose Produced by Gluconacetobacter Xylinus Strain ATCC 53524". *Cellulose*, 16, 1047-1055, 2009.
- [31] Braun D, Cherdron H, Rehahn M, Ritter H, Voit B. *Polymer Synthesis: Theory and Practice*, 5th ed. 323-373, Berlin Heidelberg, Germany, Springer-Verlag, 2013.
- [32] Filho GR, Monteiro DS, Meireles C, Assunção RMN, Cerqueira DA, Barud HS, Ribeiro SJ, Messadeq Y. "Synthesis and characterization of cellulose acetate produced from recycled newspaper". *Carbohydrate Polymers*, 73(1), 74-82, 2008.
- [33] Tonouchi N, Horinouchi S, Tsuchida T, Yoshinaga F. "Increased Cellulose Production from Sucrose by Acetobacter after Introducing the Sucrose Phosphorylase Gene". *Bioscience, Biotechnology, and Biochemistry*, 62, 1778-1780, 1998.
- [34] Molina-Ramírez C, Castro M, Osorio M, Torres-Taborda M, Gómez B, Zuluaga R, Gómez C, Gañán P, Rojas OJ, Castro C. "Effect of different carbon sources on bacterial nanocellulose production and structure using the low pH resistant strain Komagataeibacter medellinensis". *Materials*, 10, 639, 2017.
- [35] Mikkelsen D, Flanagan BM, Dykes GA, Gidley MJ. "Influence of different carbon sources on bacterial cellulose production by Gluconacetobacter xylinus strain ATCC 53524". *Journal of Applied Microbiology*, 107, 576-583, 2009.
- [36] Pourramezan GZ, Roayaei AM, Qezelbash QR. "Optimization of culture conditions for bacterial cellulose production by Acetobacter sp. 4B-2". *Biotechnology*, 8, 150-154, 2009.
- [37] Çoban EP, Biyik H. "Effect of various carbon and nitrogen sources on cellulose synthesis by Acetobacter lovaniensis HBB5". *African Journal of Biotechnology*, 10(27), 5346-5354, 2011.
- [38] Ishihara M, Matsunaga M, Hayashi N, Tişler V. "Utilization of d-xylose as carbon source for production of bacterial cellulose". *Enzyme and Microbial Technology*, 31, 986-991, 2002.
- [39] Trovatti E, Serafim LS, Freire CSR, Silvestre AJD, Neto CP. "Gluconacetobacter Sacchari: An Efficient Bacterial Cellulose Cell-Factory". *Carbohydrate Polymers*, 86, 1417-1420, 2011.
- [40] Shigematsu T, Takamine K, Kitazato M, Morita T, Naritomi T, Morimura S, Kida K. "Cellulose production from glucose using a glucose dehydrogenase gene (gdh)-deficient mutant of Gluconacetobacter xylinus and its use for bioconversion of sweet potato pulp". *Journal of Bioscience and Bioengineering*, 99(4), 415-422, 2005.
- [41] Jonas R, Farah L. "Production and application of microbial cellulose". *Polymer Degradation and Stability*, 59, 101-106, 1998.
- [42] Seto A, Kojima Y, Tonouchi N, Tsuchida T, Yoshinaga F. "Screening of bacterial cellulose producing Acetobacter strains suitable for sucrose as a carbon source". *Bioscience, Biotechnology, and Biochemistry*, 61(4), 735-736, 1997.
- [43] Masaoka S, Ohe T, Sakota N. "Production of cellulose from glucose by Acetobacter xylinum". *Journal of Fermentation and Bioengineering*, 75, 18-22, 1993.
- [44] Tsouko E, Kourmentza C, Ladakis D, Kopsahelis N, Mandala I, Papanikolaou S, Paloukis F, Alves V, Koutinas A. "Bacterial cellulose production from industrial waste and by-product streams". *International Journal of Molecular Sciences*, 16, 14832-14849, 2015.
- [45] Carreira P, Mendes J.A.S, Trovatti E, Serafim L.S, Freire C.S.R, Silvestre A.J.D, Neto C.P. "Utilization of residues from agro-forest industries in the production of high value bacterial cellulose". *Bioresource Technology*, 102, 7354-7360, 2011.
- [46] Jung HI, Lee OM, Jeong J.H, Jeon YD, Park KH, Kim HS, An WG, Son HJ. "Production and characterization of cellulose by Acetobacter sp. V6 using a cost-effective molasses-corn steep liquor medium". *Biotechnology and Applied Biochemistry*, 162(2), 486-497, 2010.
- [47] Vazquez A, Foresti ML, Cerrutti P, Galvagno M. "Bacterial cellulose from simple and low-cost production media by Gluconacetobacter xylinus". *Journal of Polymers and the Environment*, 21(2), 545-554, 2013.
- [48] Gayathry G, Gopalaswamy G. "Production and characterization of microbial cellulosic fibre from Acetobacter xylinum". *Indian Journal of Fibre and Textile Research*, 39, 93-96, 2014.
- [49] Shaikh HM, Anis A, Poulouse AM, Al-Zahrani SM, Madhar NA, Alhamidi A, Aldeligan SH, Alsubaie FS. "Synthesis and Characterization of Cellulose Triacetate Obtained from Date Palm (Phoenix dactylifera L.) Trunk Mesh-Derived Cellulose". *Molecules*, 27, 1434,1-13, 2022.
- [50] De Oliveira SA, da Silva BC, Riegel-Vidotti IC, Urbano A, de Sousa Faria-Tischer PC, Tischer CA. "Production and characterization of bacterial cellulose membranes with hyaluronic acid from chicken comb". *International Journal of Biological Macromolecules*, 97, 642-653, 2017.
- [51] Faria-Tischer PCS, Costa CAR, Tozetti I, Dall'Antonia LH, Vidotti M. "Structure and effects of gold nanoparticles in bacterial cellulose-polyaniline conductive membranes". *RSC Advances*, 6, 9571-9580, 2016.

- [52] George J, Ramana KV, Bawa AS, Siddaramaiah. "Bacterial cellulose nanocrystals exhibiting high thermal stability and their polymer nanocomposites". *International Journal of Biological Macromolecules*, 48(1), 50–57, 2011.
- [53] Barud HS, Ribeiro CA, Crespi MS, Martines MAU, Dexpert-Ghys J, Marques RFC, Ribeiro SJL. "Thermal characterization of bacterial cellulose-phosphate composite membranes". *Journal of Thermal Analysis and Calorimetry*, 87(3), 815–818, 2007.
- [54] Klemm D, Philipp B, Heinze U, Wagenknecht W. *Comprehensive Cellulose Chemistry*, Weinheim, Germany, Wiley-VCH, 1998.
- [55] Halib N, Amin M, Ahmad I. "Physicochemical properties and characterization of nata de coco from local food industries as a source of cellulose". *Sains Malaysiana*, 41(2), 205–211, 2012.
- [56] Surma-ślusarska B, Presler S. "Characteristics of bacterial cellulose obtained from *Acetobacter xylinum* culture for application in papermaking". *Fibres and Textiles in Eastern Europe*, 16(69), 108–111, 2008.
- [57] Sun JX, Xu F, Sun XF, Xiao B, Sun RC. "Physico-chemical and thermal characterization of cellulose from barley straw". *Polymer Degradation and Stability*, 88(3), 521–531, 2005.
- [58] Gabbot P. *Principles and applications of thermal analysis*. 87-118, Oxford, United Kingdom, Blackwell Publishing Ltd; 2008.
- [59] Candido RG, Godoy GG, Gonçalves AR. "Characterization and application of cellulose acetate synthesized from sugarcane bagasse". *Carbohydrate Polymers*, 167, 280-289, 2017.
- [60] Barud HS, de Araujo AM, Santos DB, de Assuncao RMN, Meireles CS, Cerqueira DA, Rodrigues G, Ribeiro CA, Messaddeq Y, Ribeiro SJL. "Thermal behavior of cellulose acetate produced from homogeneous acetylation of bacterial cellulose". *Thermochim Acta*, 471, 61–69, 2008.
- [61] Yamamoto H, Horii F, Hirai A. "Structural studies of bacterial cellulose through the solid-phase nitration and acetylation by CP/MAS ¹³C NMR spectroscopy". *Cellulose*, 13, 327-342, 2006.
- [62] Kim DY, Nishiyama Y, Kuga S. "Surface acetylation of bacterial cellulose". *Cellulose*, 9, 361–367, 2002.
- [63] Tabuchi M, Watanabe K, Morinaga Y, Yoshinaga F. "Acetylation of bacterial cellulose: preparation of cellulose acetate having a high degree of polymerization". *Bioscience, Biotechnology, and Biochemistry*, 62(7), 1451–1454, 1998.
- [64] Kotatha D, Morishima K, Uchida S, Ogino M, Ishikawa M, Futuike T, Tamura H. "Preparation and characterization of gel electrolyte with bacterial cellulose coated with alternating layers of chitosan and alginate for electric double-layer capacitors". *Research on Chemical Intermediates*, 44(8), 4971–4987, 2018.
- [65] Ccorahua R, Troncoso OP, Rodriguez S, Lopez D, Torres FG. "Hydrazine treatment improves conductivity of bacterial cellulose/graphene nanocomposites obtained by a novel processing method". *Carbohydrate Polymers*, 171, 68–76, 2017.
- [66] Zhou ZH, Yang YB, Han YY, Guo QQ, Zhang XX, Lu CH. "In situ doping enables the multifunctionalization of templately synthesized polyaniline@cellulose nanocomposites". *Carbohydrate Polymers*, 177, 241–248, 2017.
- [67] Lee SH, Lim YM, Jeong SI, An SJ, Kang SS, Jeong CM, Huh JB. "The effect of bacterial cellulose membrane compared with collagen membrane on guided bone regeneration". *The Journal of Advanced Prosthodontics*, 7(6), 484-495, 2015.
- [68] Feng Y, Zhang X, Shen Y, Yoshino K, Feng W. "A mechanically strong, flexible and conductive film based on bacterial cellulose/graphene nanocomposite". *Carbohydrate Polymers* 87(1), 644–649, 2012.
- [69] Liang HW, Guan QF, Zhu Z, Song LT, Yao HB, Lei X, Yu SH. () "Highly conductive and stretchable conductors fabricated from bacterial cellulose". *NPG Asia Materials*, 4, 34, 2012.
- [70] Shi Q, Li Y, Sun J, Zhang H, Chen L, Chen B, Yang H, Wang Z. "The osteogenesis of bacterial cellulose scaffold loaded with bone morphogenetic protein 2". *Biomaterials*, 33, 6644–6649, 2012.
- [71] Hu W, Chen S, Yang Z, Liu L, Wang H. "Flexible electrically conductive nanocomposite membrane based on bacterial cellulose and polyaniline". *The Journal of Physical Chemistry B*, 115(26), 8453–8457, 2011.
- [72] Takanoglu D, Yılmaz K, Ozcan Y, Karabulut O. "Structural, electrical and optical properties of thermally evaporated CdSe and In-doped CdSe thin films". *Chalcogenide Letters*, 12, 35–42, 2015.